
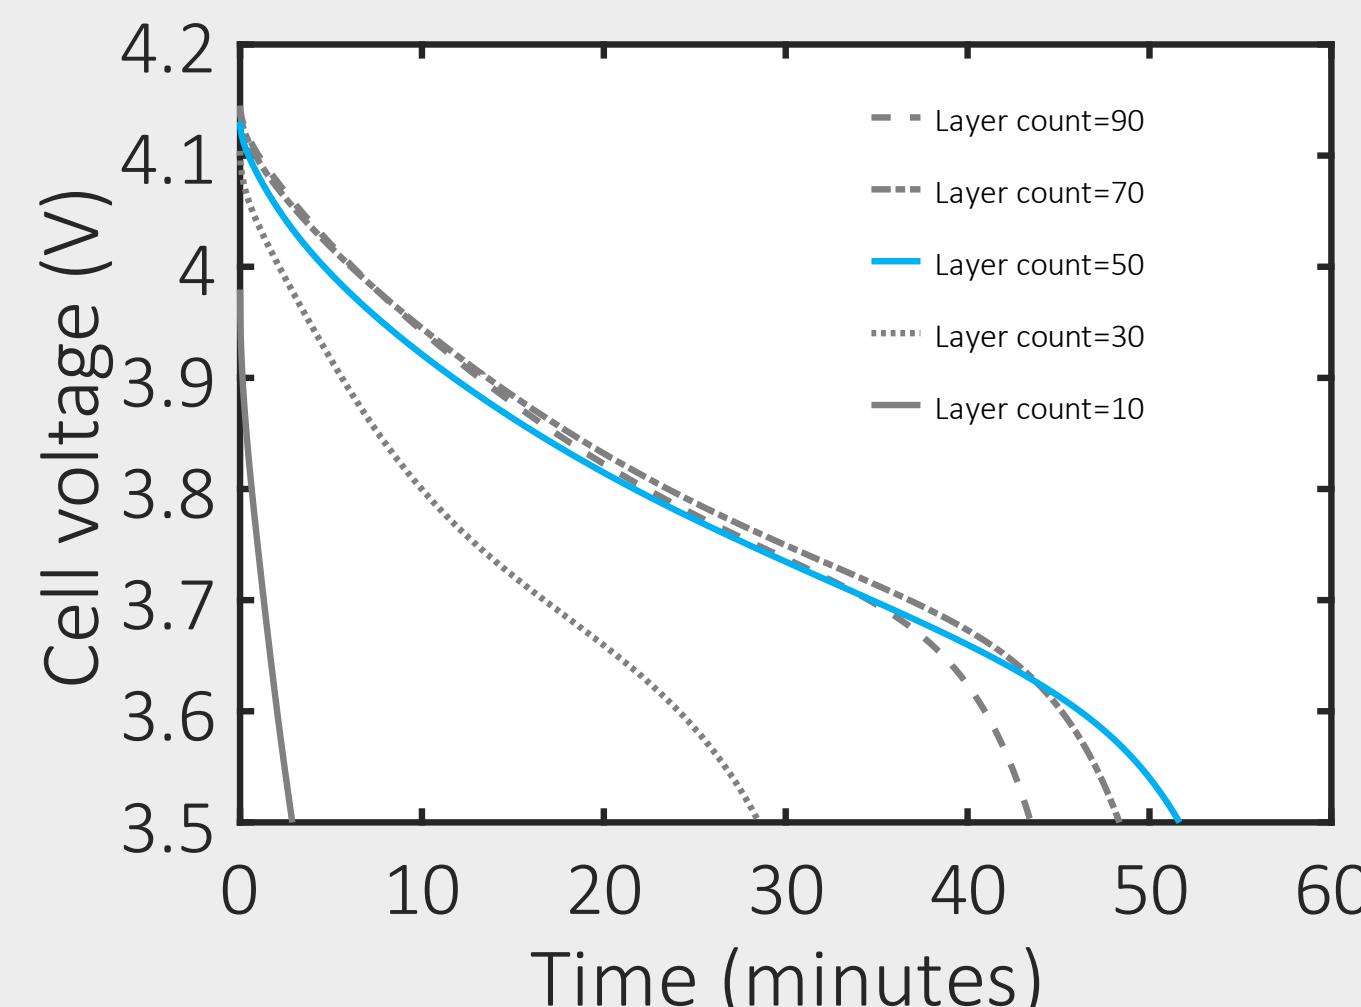
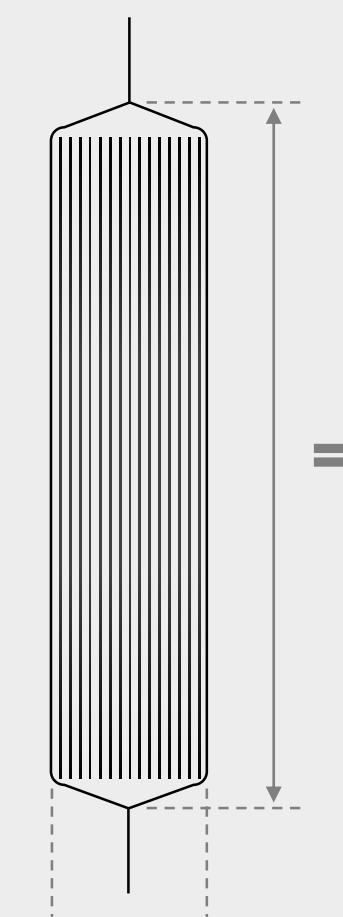


Optimising Li-ion Cell Layers

Rapid Cell Design For EV Fast Charging

Ian D. Campbell*, Krishnakumar Gopalakrishnan, Dr. Monica Marinescu,
Dr. Marcello Torchio, Dr. Gregory J. Offer, Prof. Davide Raimondo

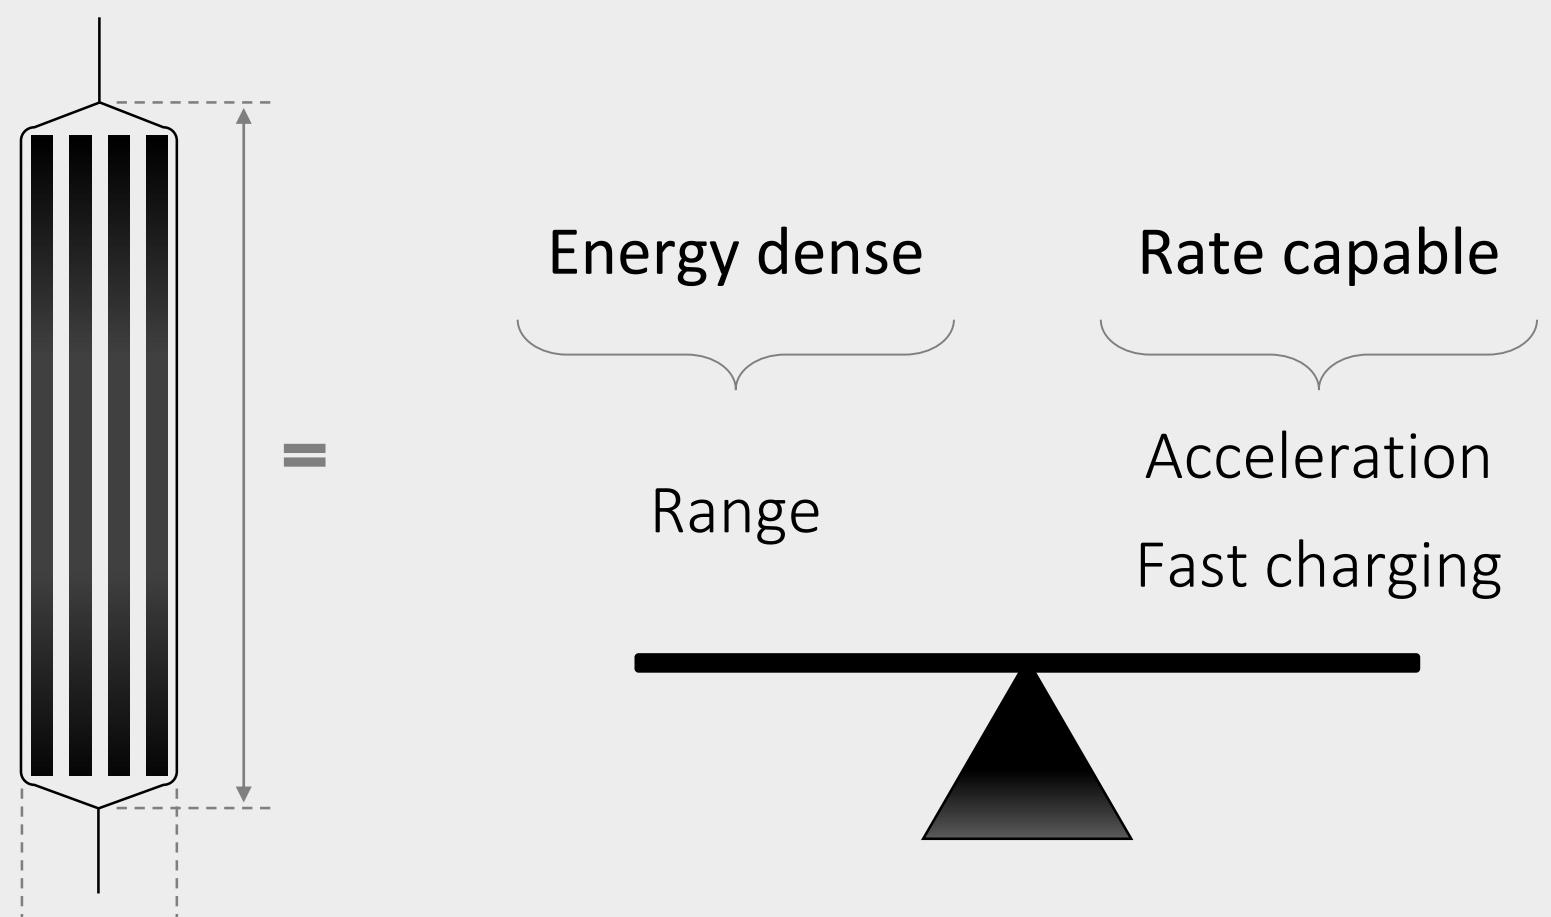

[LEARN MORE](#)

ENERGY & POWER BALANCE

- Conflicting requirements pose a layer optimisation problem
- Desire trading of energy & power in equally-dimensioned cells
- Layer reconfiguration trades fraction of active material mass with surface area available for redox reaction
- Maximum usable energy is available for neither the most rate capable nor most energy density layer configuration
- Empirical determination of optimal layer count is slow, costly & may not provide energy-density maximising result
- We propose a rapid & inexpensive model-based alternative

LAYER OPTIMISATION

- Stack thickness & active & inactive material quantities are recalculated for each new layer count (n) using derived expressions
- The optimal (i.e. range-maximising) layer configuration is the minimum number of layers that meets EV acceleration and fast charging targets
- Initially, we gain a lot of rate capability for little energy density loss since power density per layer decreases faster than cell nominal capacity
- At higher layer counts it becomes increasingly expensive, in terms of energy density sacrificed, to accommodate higher powers
- Efficient designs employ < half the maximum possible number of layers

$$L_{stack} = \sum_j L_j(n) + L_{Al}(n) + L_{Cu}(n)$$


... $\forall n \in \mathbb{N}, j \in \{pos, sep, neg\}$

$$L_j(n) = nl_j$$

$$L_{Al}(n) = \begin{cases} \left(\frac{n}{2}\right) l_{Al}, & \text{if } n \text{ is even} \\ \left(\frac{n+1}{2}\right) l_{Al}, & \text{if } n \text{ is odd} \end{cases}$$

$$L_{Cu}(n) = \begin{cases} \left(\frac{n+2}{2}\right) l_{Cu}, & \text{if } n \text{ is even} \\ \left(\frac{n+1}{2}\right) l_{Cu}, & \text{if } n \text{ is odd} \end{cases}$$

[LEARN MORE](#)

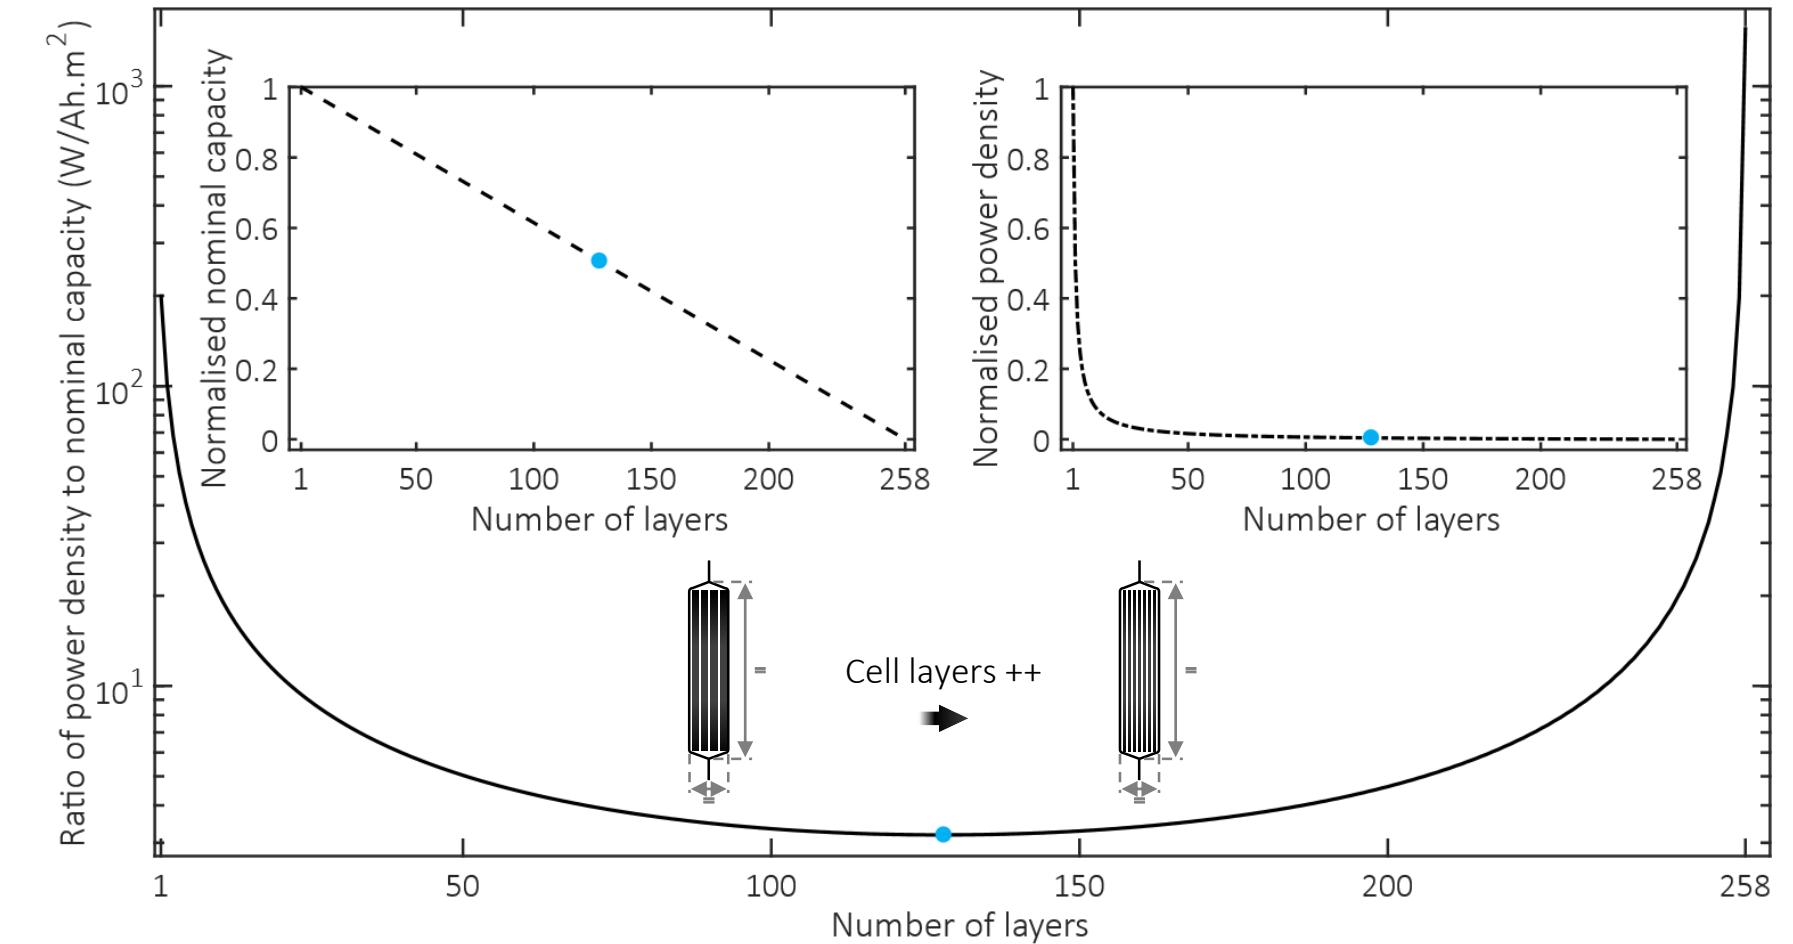

Li-PLATING PROTECTED FAST CHARGE

- Specify desired xEV configuration & define performance criteria
- Cells undergo simulated vehicle acceleration & fast charging
- Charge time is minimised with a constant power strategy
- Design for highest powers & impose Li concentration limit, C_{sat}
- Cell designs exhibit Li-plating protection & max. energy density
- Individual domain thicknesses are recomputed using stack thickness & a fixed, capacity-balanced, electrode thickness ratio

1 Define vehicle

xEV platform PHEV

Powertrain - (series)

Module & cell configuration 8S1P (mod.)
12S1P (cells)

xEV mass (w/o cells) 1,654 kg (inc. ICE)

Fast charge SOC range 30 - 80 %

2 Define criteria

Fast charging Acceleration

$T(t) < T_{max}$ $T(t_f) < T_{max}$

$V(t) < V_{max}$ $V(t_f) > V_{min}$

$z(t) \geq z^*$ $z(t_f) > z_{min}$

$C_s^*(t) < C_{sat}$

$t < t_{max}$

$$l_{ce} = \frac{L_{stack} - [0.5(n+1)]l_{cu} - [0.5n]l_{al}}{n} - l_{sep}$$

$$l_{ratio} = \frac{l_{neg}}{l_{pos}} = \frac{\varepsilon_{pos}}{\varepsilon_{neg}}$$


$$l_{neg} = l_{ce} - l_{pos}$$

$$l_{pos} = \frac{l_{ce}}{l_{ratio} + 1}$$

[LEARN MORE](#)

P2D SIMULATION

- Custom, efficient binary search screens layer configurations
- Open-source electrochemical P2D model directly accepts power input, solves for current & converges rapidly owing to Jacobian generated using algorithmic differentiation
- Each new layer configuration requires model updates
- Vector of layer State-of-Functions is produced; lowest layer count with a unity SoF is the optimal

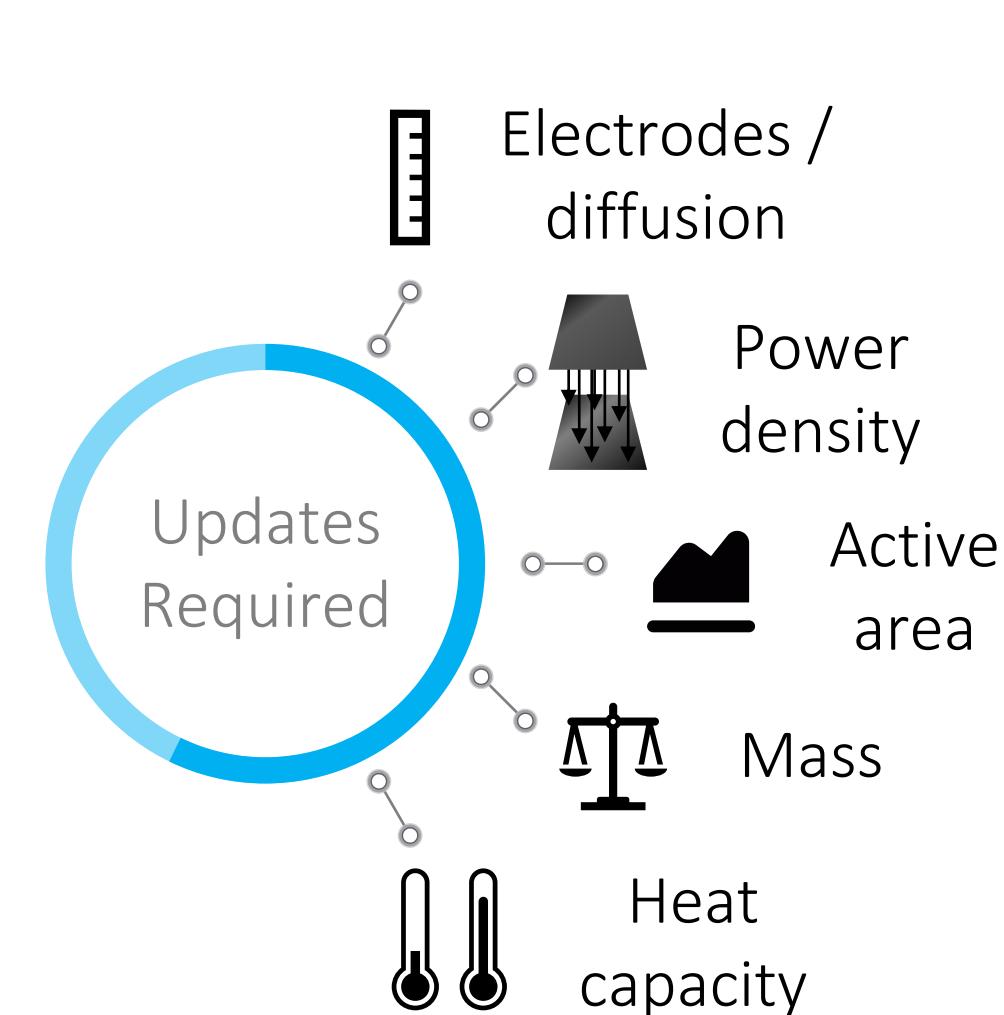

$$\frac{-\sigma_{effpos}\Phi_{s_0}^2}{\Delta x_{pos}} + \frac{\sigma_{effneg}\Phi_{s_n}^2}{\Delta x_{neg}} + \frac{\sigma_{effpos}\Phi_{s_0}\Phi_{s_1}}{\Delta x_{pos}} + \frac{\sigma_{effneg}\Phi_{s_n}\Phi_{s_{n-1}}}{\Delta x_{neg}} + p - a_{s_{pos}}F_{j_0}x_{pos}\Phi_{s_0} - a_{s_{neg}}F_{j_n}x_{neg}\Phi_{s_n} = 0$$

Direct power input


Workflow →

P2D model

Workflow →


System Jacobian for rapid convergence

$$J_{ij} = \frac{\delta f_i}{\delta x_j}$$

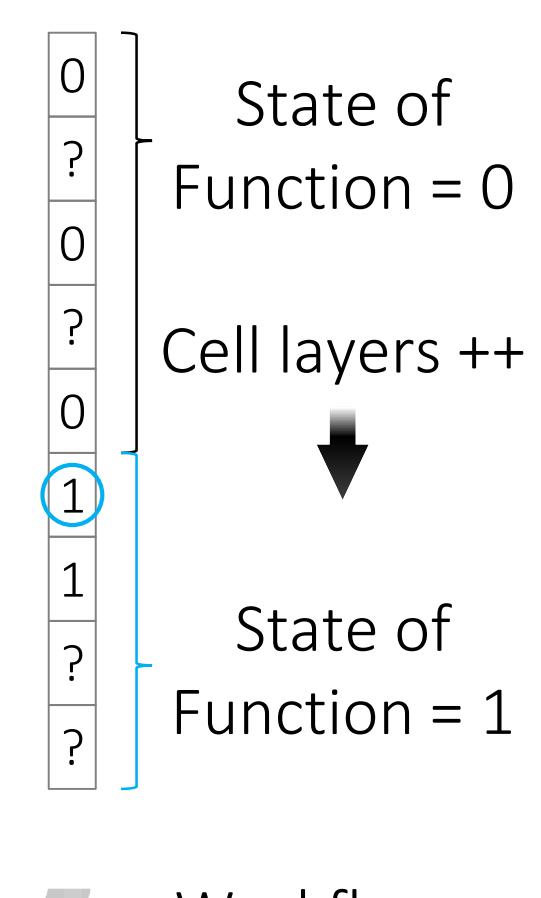


Workflow

Highest layer counts required at coldest condition in response to slow Li diffusion in graphite

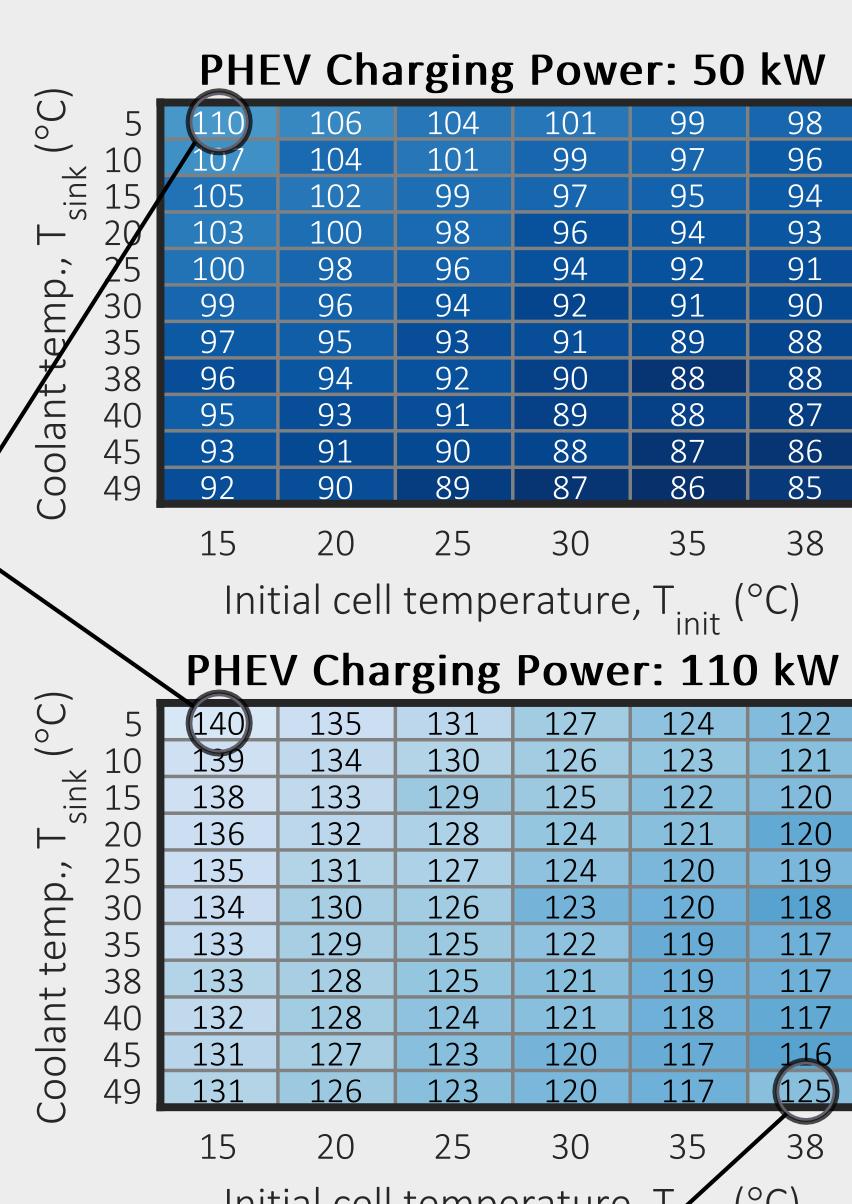

More layers required at higher temps to curtail heat generation (less Watts/layer)

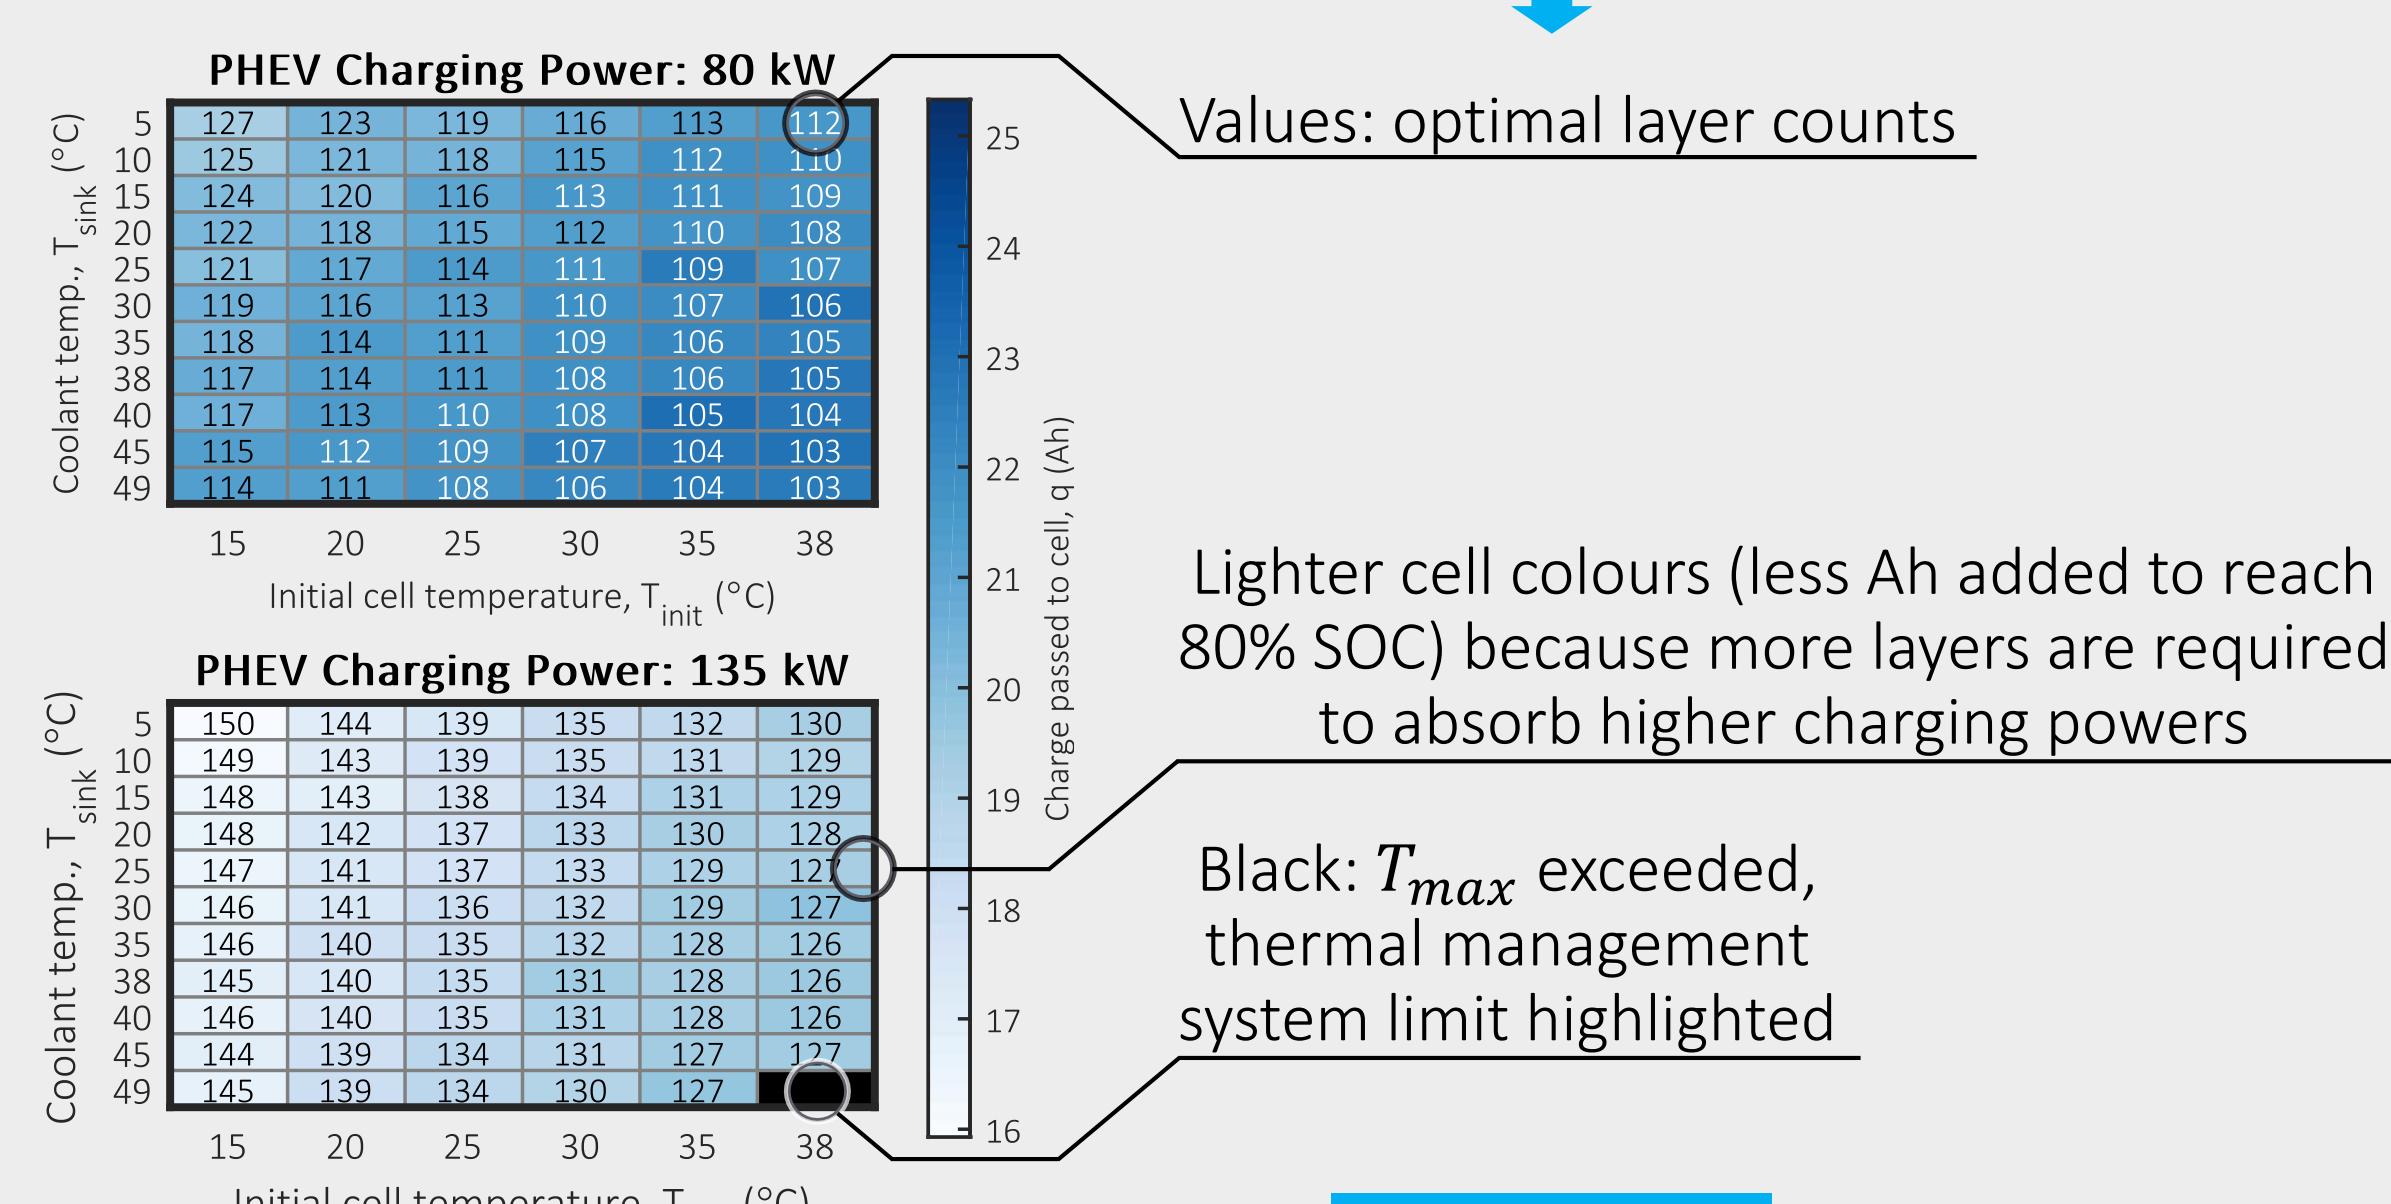


[LEARN MORE](#)

COMMON MODULE DESIGN FOR EV PACKS

- New layer configurations generated for a different vehicle platform, using a cell with identical external dimensions
- Produces energy-density maximising designs for this new vehicle.. ..and enables common battery pack module design across both/many platforms, lowering R&D costs & time to market for automotive OEMs

Cell colour: 8S3P BEV pack layout provides more nominal capacity, lowering the E-rate during charge.

With less power-per-cell-layer, we need fewer layers & can design more energy dense cells vs. PHEV configuration

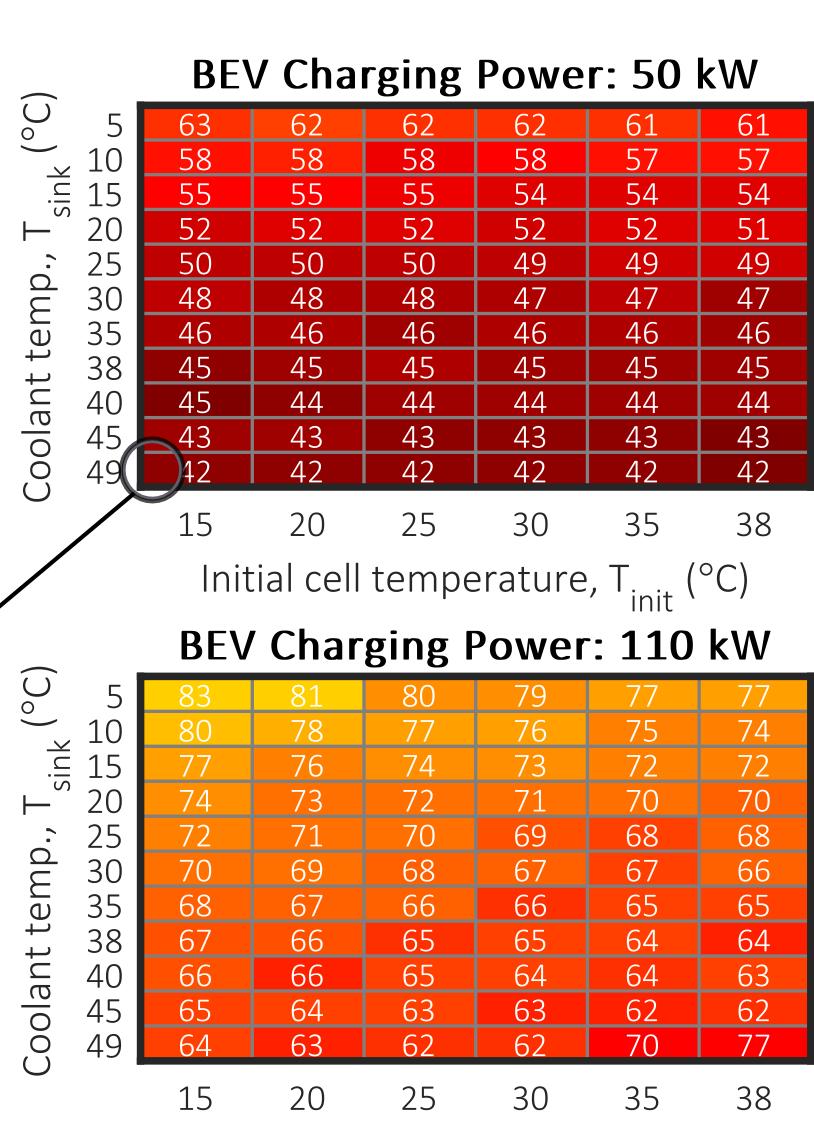

TAILORED CELL DESIGN MAPS

- Repeat for new coolant (ambient) & cell temperatures to generate cell design maps precisely tailored to vehicle fast charge targets
- Values in coloured cells are optimal layer configurations/counts
- Map colour is usable capacity; charge added, 30 – 80 % SOC window
- Black colours indicate unsuitable cell materials & thermal management system for specified temperatures & design targets
- Faster & lower cost than iterative, empirical cell development
- Method can offer xEV range extension over empirical cell designs by producing energy-density optimised layer configurations

1 Define another vehicle

xEV platform BEV

Powertrain (all-electric)

Module & cell configuration 8S3P (mod.)

12S1P (cells)

xEV mass (w/o cells) 1,687 kg

Fast charge SOC range 20 - 80 %